

On the velocity-strengthening behavior of dry friction

Yohai Bar-Sinai¹, Robert Spatschek², Efim A. Brener^{1,3} and Eran Bouchbinder¹

¹*Chemical Physics Department, Weizmann Institute of Science, Rehovot 76100, Israel*

²*Max-Planck-Institut für Eisenforschung GmbH, D-40237 Düsseldorf, Germany*

³*Peter Grünberg Institut, Forschungszentrum Jülich, D-52425 Jülich, Germany*

The onset of frictional instabilities, e.g. earthquakes nucleation, is intimately related to velocity-weakening friction, in which the frictional resistance of interfaces decreases with increasing slip velocity. While this frictional response has been studied extensively, much less attention has been given to steady-state velocity-strengthening friction, in spite of its importance for various aspects of frictional phenomena such as the propagation speed of interfacial rupture fronts and the amount of stored energy released by them. In this note we suggest that a crossover from steady-state velocity-weakening friction at small slip velocities to steady-state velocity-strengthening friction at higher velocities might be a generic feature of dry friction. We further argue that while thermally activated rheology naturally gives rise to logarithmic steady-state velocity-strengthening friction, a crossover to stronger-than-logarithmic strengthening might take place at higher slip velocities, possibly accompanied by a change in the dominant dissipation mechanism. We sketch a few physical mechanisms that may account for the crossover to stronger-than-logarithmic steady-state velocity-strengthening. Finally, we compile a rather extensive set of experimental data available in the literature, which lends support to these ideas.

I. INTRODUCTION

Understanding the constitutive behavior of dry frictional interfaces has far-reaching implications for a broad range of phenomena and scientific disciplines [1–12]. It is well-established that the onset of frictional instabilities, which might lead to interfacial failure (e.g. earthquakes), is intimately related to weakening effects, i.e. the reduction of frictional resistance with increasing slip displacement or slip velocity. In particular, when the slip velocity v is regarded as a basic frictional control variable, the variation of the steady-state frictional resistance with v is of great importance. Naturally, steady-state velocity-weakening (denoted hereafter as SVW) friction has been studied extensively. On the other hand, much less attention has been given to steady-state velocity-strengthening (denoted hereafter as SVS) friction, in which the steady-state frictional resistance increases with increasing v . This behavior might affect, for example, the propagation speed of rupture fronts, their propagation distance and the amount of stored energy released by them. Our goal in this note is to discuss SVS friction, its functional form and possible physical origins, and to point out direct evidence for its existence based on experimental data available in the literature.

The interface between two macroscopic bodies in dry frictional contact is typically composed of an ensemble of contact asperities whose total area A_r is orders of magnitude smaller than the nominal contact area A_n . The real contact area typically depends on the time elapsed since a contact was formed, i.e. on the contact's "age" (or "maturity") typically quantified by a state variable of time dimension ϕ [8, 13–16], an idea that dates back at least to Rabinowicz [17]. The frictional stress (resistance) τ is proportional to $A_r(\phi)$ [18]. The proportionality factor depends on the slip velocity v and possibly on a set of internal state variables which we schematically denote by

θ , and can be interpreted as the shear strength $\sigma_s(\theta, v)$ (related to the plastic flow of contact asperities) [8, 18]. This contribution to the frictional resistance is rheological in nature. Putting the two together, one can write the frictional stress (resistance) as [8, 18]

$$\tau(\phi, \theta, v) = \frac{A_r(\phi) \sigma_s(\theta, v)}{A_n}. \quad (1)$$

During steady-state sliding at a velocity v , the internal state variables attain unique values $\phi(v)$ and $\theta(v)$. Therefore, under steady-state conditions the frictional stress $\tau^{ss}(v)$ takes the form

$$\tau^{ss}(v) = \frac{A_r[\phi(v)] \sigma_s[\theta(v), v]}{A_n}. \quad (2)$$

In this note we focus on the variation of $\tau^{ss}(v)$ with v , and in particular on the sign of $\partial_v \tau^{ss}$, its dependence on v and its functional form. $\partial_v \tau^{ss} < 0$, i.e. SVW friction, is known to facilitate unstable accelerating slip and frictional instabilities [2, 14]. On the other hand, $\partial_v \tau^{ss} > 0$, i.e. SVS friction, might promote stable slip, limit the propagation speed of interfacial rupture fronts and affect the magnitude of slip events [19–25], limit the seismogenic zone [26] and affect earthquake afterslip and stress drops [27]. In what follows we suggest that SVS friction, $\partial_v \tau^{ss} > 0$, generically emerges in dry friction over some range of slip velocities, discuss its possible physical origins and the available experimental evidence for its existence.

II. REAL CONTACT AREA AGING AND ITS SATURATION DURING SLIDING

Equation (2) suggests that the steady-state frictional stress $\tau^{ss}(v)$ is a product of a steady-state real contact

of area contribution $A_r^{ss}(v) \equiv A_r[\phi(v)]$ and a rheological contribution $\sigma_s^{ss}(v) \equiv \sigma_s[\theta(v), v]$. As the latter is assumed to be an increasing function of v , $\partial_v \sigma_s^{ss} > 0$ (to be discussed later), we focus first on $A_r^{ss}(v)$.

The physical argument we present has already appeared in the work of Baumberger, Caroli and coworkers [8, 28, 29] and in Bar-Sinai et al. [23]. It is repeated here briefly for completeness. The starting point is the non-steady behavior of $A_r(\phi)$ in the absence of slip, $v=0$. In this case, ϕ grows linearly with the time t elapsed since the frictional interface was formed (when the bodies under consideration brought into frictional contact) or since previous slip halted, $\phi=t$.

It is well-established that under these conditions the real contact area undergoes logarithmic aging, i.e. $A_r(t)$ increases logarithmically, a behavior observed in many materials [3, 8, 13–15, 30–33]. Specifically, the time evolution of $A_r(t)$ was observed to take the form

$$A_r(t) \propto 1 + b \log(t/\phi^*), \quad (3)$$

where b and ϕ^* are constants [13, 14] (The proportionality factor is linear in the normal stress σ_n). This expression, however, cannot be valid for arbitrarily short times as it becomes singular for $t \rightarrow 0$, which is of course unphysical. This simply means that $A_r(t)$ actually takes the form

$$A_r(t) \propto 1 + b \log(1 + t/\phi^*). \quad (4)$$

where ϕ^* can be interpreted as a typical cutoff time scale for the onset of logarithmic aging. Equation (3) provides a good approximation for Eq. (4) when $t \gg \phi^*$, but completely fails in the opposite limit, $t \ll \phi^*$. These features were verified experimentally [32–34].

While this might appear as a somewhat academic discussion of a short time regularization of the logarithmic aging formula, and indeed it is almost always overlooked, this is not the case. To see the relevance of this short time regularization for our purposes here, we should consider steady sliding at a velocity v . Since ϕ quantifies the age of the real contact it must be a decreasing function of v (the “lifetime” of a contact asperity is shorter the higher the slip velocity, i.e. “rejuvenation”). It is well established that under steady-state conditions [8, 13, 28]

$$\phi = D/v, \quad (5)$$

where D is a typical slip distance (usually related to the contact asperities size) [3, 8]. Therefore, under steady-state sliding conditions the real contact area takes the form

$$A_r^{ss}(v) \propto 1 + b \log\left(1 + \frac{D}{v\phi^*}\right). \quad (6)$$

This implies that $A_r^{ss}(v)$ decreases logarithmically with increasing v for $v \lesssim D/\phi^*$ and that it approaches a constant (saturates) for $v \gg D/\phi^*$. Therefore, if indeed the rheological contribution to the steady-state frictional resistance increases with v , $\partial_v \sigma_s^{ss} > 0$, we conclude

that *irrespective* of the precise form of $\sigma_s^{ss}(v)$ we expect $\partial_v \tau^{ss} > 0$ for $v \gg D/\phi^*$. This is an important observation.

III. LOGARITHMIC STEADY-STATE VELOCITY-STRENGTHENING FRICTION

The last section concluded with the observation that the steady-state frictional stress (resistance) $\tau^{ss}(v)$ is expected to become velocity-strengthening above a certain slip velocity $\sim D/\phi^*$ due to the saturation of the real contact area, assuming $\partial_v \sigma_s^{ss} > 0$. Our goal in this section, and the subsequent one, is to discuss the latter.

The standard approach to the velocity dependence of the rheological part of the frictional stress (“shear strength”) is to attribute it to thermal activation [8, 16, 28]. We briefly repeat the argument here as it sets the stage for what will follow. The starting point is to treat the real contact of area $A_r(\phi)$ as fixed, to neglect any rheological internal variables θ and to assume that v is a result of a stress-biased thermally activated process such that

$$v = v_0 \left(\exp\left[-\frac{\Delta(\tau)}{k_B T}\right] - \exp\left[-\frac{\Delta(-\tau)}{k_B T}\right] \right). \quad (7)$$

Here v_0 is a reference velocity scale related to a basic attempt rate and an intrinsic length scale, $\Delta(\tau)$ is a stress-biased activation barrier, k_B is Boltzman’s constant and T is the temperature. The second exponential appears in order to account for backwards transitions (implying a proper $\tau \rightarrow -\tau$ symmetry and consistency with the second law of thermodynamics).

The stress-biased activation barrier is assumed to take the form

$$\Delta(\tau) = E_0 - \Omega \tau^{loc}(\tau), \quad (8)$$

where E_0 is the bare energy barrier, Ω is the activation volume (typically much larger than atomic volumes, i.e. corresponding to a collective multi-atom process [8, 16]) and $\tau^{loc}(\tau) = A_n \tau / A_r$ is the local stress at the asperity level. Note that the local asperity stress τ^{loc} is significantly enhanced compared to the macroscopic stress τ by a large factor $A_n/A_r \gg 1$. Therefore, we can rewrite Eq. (7) as

$$v = 2 v_0 \exp\left[-\frac{E_0}{k_B T}\right] \sinh\left(\frac{A_n \Omega \tau}{A_r k_B T}\right), \quad (9)$$

which can be inverted in favor of the stress to read (putting back the ϕ dependence of A_r)

$$\tau(\phi, v) = \frac{k_B T A_r(\phi)}{\Omega A_n} \sinh^{-1}\left(\frac{v}{2 v_0} \exp\left[\frac{E_0}{k_B T}\right]\right). \quad (10)$$

Finally, since E_0 is typically much larger than $k_B T$, we can treat the argument of the inverse sinh-function as

large for all v 's of interest and approximate $\sinh^{-1}(x) \simeq \log(2x)$, yielding

$$\tau(\phi, v) = \frac{A_r(\phi)}{A_n} \left[\frac{E_0}{\Omega} + \frac{k_B T}{\Omega} \log \left(\frac{v}{v_0} \right) \right]. \quad (11)$$

The frictional stress in Eq. (11) takes the form assumed in Eq. (1) and $\sigma_s(v)$ can be readily identified. Equation (11) predicts that the instantaneous response (i.e. faster than the typical evolution time of ϕ) of the frictional stress to slip velocity “jumps” would be logarithmic in the ratio between the final and the initial v 's. This logarithmic “direct effect” [3, 8] has been observed for many materials in a wide range of slip velocities v , but typically not larger than a few hundreds of $\mu\text{m}/\text{sec}$.

What are the implications of Eq. (11) for the steady-state frictional stress $\tau^{ss}(v)$? To answer this question one should substitute $A_r^{ss}(v)$ of Eq. (6) for $A_r(\phi)$ in Eq. (11). For $v \ll D/\phi^*$, the v -dependence of $\tau^{ss}(v)$ is logarithmic (neglecting $\log^2(v)$ terms) with a pre-factor whose sign depends on the relative magnitude of b and $k_B T/E_0$. In particular, for $b > k_B T/E_0$ friction is velocity-weakening and for $b < k_B T/E_0$ friction is velocity-strengthening in this range of slip velocities. In the former case, steady-state friction is velocity-weakening for $v \ll D/\phi^*$ and then it crosses over to velocity-strengthening behavior for $v \gg D/\phi^*$, when $A_r(\phi)$ approaches a constant. Therefore, the most important implication of Eqs. (6) and (11) for our purposes here is that they predict that steady-state friction is logarithmically velocity-strengthening for $v \gg D/\phi^*$. This is often overlooked in the literature, but see Baumberger and Caroli [8], Bureau et al. [29].

In Fig. 1a-b we present examples from the available literature in which logarithmic SVW friction crosses over to logarithmic SVS behavior at some slip velocity v_m (where the curve reaches a minimum). The data in Fig. 1c also exhibit logarithmic SVS.

IV. STRONGER-THAN-LOGARITHMIC STEADY-STATE FRICTION

As discussed above, a simple thermal activation model predicts the existence of logarithmic SVS friction above a slip velocity $\sim D/\phi^*$. This model assumes a single activation barrier and a single attempt rate; many of the materials of interest, however, are disordered and hence a distribution of activation barriers and time scales might be relevant. Moreover, the linear dependence of the activation barrier on τ in Eq. (8) might not be always valid. In spite of these simplifications and possible limitations, we adopt this framework and ask whether the logarithmic velocity-strengthening behavior might break down at some point.

Obviously, the simple thermal activation process breaks down when the stress-biased barrier in Eq. (8) becomes comparable to $k_B T$. Alternatively, the breakdown occurs when the slip velocity v is not much smaller

than v_0 in Eq. (7). There is, however, no easy way to independently estimate both v_0 and E_0 , which are coupled in Eq. (11). Moreover, as E_0 appears in the exponential, small variations in it can be compensated by a huge variation in v_0 , which suggests a large uncertainty in the latter. Nevertheless, some arguments for independently estimating v_0 have appeared in the literature. For example, Rice et al. [16] estimated v_0 for rocks (quartzite and granite) to be in the mm/sec range, which sets an upper bound for the validity of the thermal activation process and hence for logarithmic velocity-strengthening (assuming, for the moment, that $v_0 > D/\phi^*$).

What happens for larger slip velocities, $v \gtrsim v_0$, when thermal activation breaks down? While we suspect that the answer might be material-specific, we believe that rather generically steady-state friction remains velocity-strengthening in this regime (at least until thermal weakening possibly intervenes, see Section VI), with a functional dependence which is typically *stronger than logarithmic*. Our basic argument is that the breakdown of the thermal activation process should also signal a change in the dominant energy dissipation mechanism associated with frictional dynamics. Since logarithmic velocity-strengthening is usually intimately linked to thermal activation, we see no reason for other dissipative processes to give rise to such a weak (i.e. logarithmic) dependence on v and hence expect the dependence to be stronger than logarithmic.

While we do not aim here at developing a detailed model of the crossover to stronger-than-logarithmic steady-state friction, we would like to sketch a few possible physical scenarios that might give rise to such a behavior. We first consider the possibility that logarithmic SVS friction crosses over to a linear behavior in which $\tau^{ss} \propto v$ (see, for example, Fig. 1g and Fig. 15 in Baumberger and Berthoud [28]). This viscous-friction behavior might emerge as a standard viscous process obtained through linearization of a different thermally activated process, characterized by an activation volume significantly smaller than Ω . That is, if at high slip velocities (hence higher stresses) the physics of frictional dissipation changes such that the activation volume Ω decreases from a multi-atom/super-molecular value to an atomic/molecular volume, the thermal activation formula of Eq. (10) remains valid, but now $\Omega \tau^{loc} \ll k_B T$ (recall that $\tau^{loc} = A_n \tau / A_r$) and linearization leading to $\tau \propto v$ is sensible [35].

Another mechanism that may lead a crossover to a linear viscous behavior is well-known in the context of dislocation mechanics [36]. In this case, at relatively small mean dislocation velocities and applied stresses, dislocation motion is thermally activated with the barriers determined by local obstacles of various types and the Peierls lattice potential. At higher velocities and stresses, interactions with phonons and electrons control dislocation motion, leading to a linear drag-like relation between the stress and the velocity [37, 38]

A crossover from a thermally activated regime at

low slip velocities to a non-thermally activated regime at higher slip velocities has been briefly discussed in Baumberger and Caroli [8]. The idea there was that plastic rearrangements at contact asperities give rise to mesoscopic stress fields that perturb nearby regions. The accumulated effect of these random spatiotemporal perturbations, originating from various plastic rearrangements taking place at different locations and times, can be regarded as a dynamical/mechanical noise, which acts in parallel to the ordinary thermal noise. This dynamical/mechanical noise becomes more intense as v increases and eventually takes over the thermal noise. While the precise functional form of the velocity-strengthening frictional response associated with the dynamical/mechanical noise-controlled regime has not been discussed, it was implied that it is stronger than the logarithmic dependence associated with the thermal noise-controlled regime (cf. Fig. 17 in Baumberger and Caroli [8]).

Another physical scenario for the velocity-strengthening frictional response in the non-thermally activated regime might be based on applying Bagnold's scaling arguments, originally developed in the context of dense granular flows [39], to atomic/molecular systems [40]. The idea is that when thermal activation is irrelevant, the system has no characteristic energy scale and flow rates are controlled by collisions between hard-core-like objects, where the detailed molecular interactions are not playing a central role. In this case, the frictional stress τ is proportional to the product of the momentum transfer per collision and the rate of collisions, both linear in v , leading to $\tau \propto v^2$. While the application of Bagnold's scaling arguments to atomic/molecular systems might be questionable, our goal here is just to highlight another known mechanism for a velocity-strengthening type of response.

In strictly athermal frictional interfaces, e.g. frictional interfaces composed of granular materials such as fault gouge, where the elementary units are macroscopic and no thermal motion takes place, we do not expect logarithmic velocity-strengthening to emerge. In this case, one might expect logarithmic velocity-weakening friction at small slip velocities, due to logarithmic aging of the contacts between grains, to cross over to a stronger-than-logarithmic velocity-strengthening friction associated with nonlinear plastic rheology. This is precisely what has been observed and discussed very recently in Kuwano et al. [41] (see also Fig. 1h).

This qualitative discussion of possible physical mechanisms that might give rise to stronger-than-logarithmic velocity-strengthening friction when thermal activation breaks down is only meant to show that such mechanisms are conceivable. The generic picture that emerges is that in thermal systems, when v_0 is sufficiently larger than D/ϕ^* and $b > k_B T/E_0$, we expect logarithmic SVW friction to cross over to logarithmic SVS friction at slip velocities $v \gtrsim D/\phi^*$, which in turn crosses over to stronger-than-logarithmic velocity-strengthening fric-

tion at slip velocities $v \gtrsim v_0$. When $v_0 < D/\phi^*$, we expect logarithmic SVS friction to cross over to stronger-than-logarithmic velocity-strengthening friction, not due to the saturation of the real contact area, but rather because stronger-than-logarithmic strengthening takes over logarithmic weakening. This is also the case for strictly athermal frictional interfaces.

To conclude this section, we note that while the discussion above – starting with Eq. (1) – has focussed primarily on frictional interfaces whose contact asperities deform plastically, a similar picture has been discussed by Byerlee in the context of frictional interfaces composed of geological materials governed by brittle fracture of asperities [42]. Moreover, we would like to draw the readers' attention to the work of Estrin and Bréchet [43], who seem to discuss somewhat related ideas. Finally, it is important to mention that in the context of lubrication, i.e. frictional interfaces that contain fluids, the generic steady-state dry friction curve $\tau^{ss}(v)$ discussed here is the standard known as the ‘‘Stribeck curve’’ [4, 44]. In this curve, solid contact dominates at small slip velocities and hydrodynamic viscous friction dominates at high slip velocities, with a mixed regime in between, where friction goes through a minimum.

V. EXPERIMENTAL EVIDENCE

To test the physical picture described above, we have searched the available literature, looking for steady-state friction experiments that go up to sufficiently high slip velocities. While these experiments are not easy to perform, and sometimes require to employ different experimental techniques in different ranges of slip velocities, we have been able to trace quite a few examples that lend support to the proposed picture. All of the panels of Fig. 1, which span a rather wide range of materials, clearly exhibit SVS. Here we provide additional information about the data presented in the figure:

- (a) $\tau^{ss}(v)$ for a pre-cut fault in halite in a triaxial apparatus, data extracted from Fig. 3 of Shimamoto [45]. The lower panel corresponds to a normal stress of $\sigma_n = 50\text{MPa}$ and the upper one to $\sigma_n = 100\text{MPa}$. A crossover from logarithmic SVW (marked by a negative slope green dashed line) to logarithmic SVS (marked by a positive slope red dotted line) is observed. At yet higher normal stresses no SVW is observed (not shown).
- (b) $\mu^{ss}(v) \equiv \tau^{ss}(v)/\sigma_n$ for an interface between rough PMMA (a glassy polymer) and smooth silanized glass, data extracted from Fig. 7 of Bureau et al. [29]. A clear crossover from logarithmic SVW to logarithmic SVS is observed. Note that the smoothness of the substrate (a rigid silanized glass) implies that contact asperities are not continuously formed and destroyed during sliding, and hence that a different

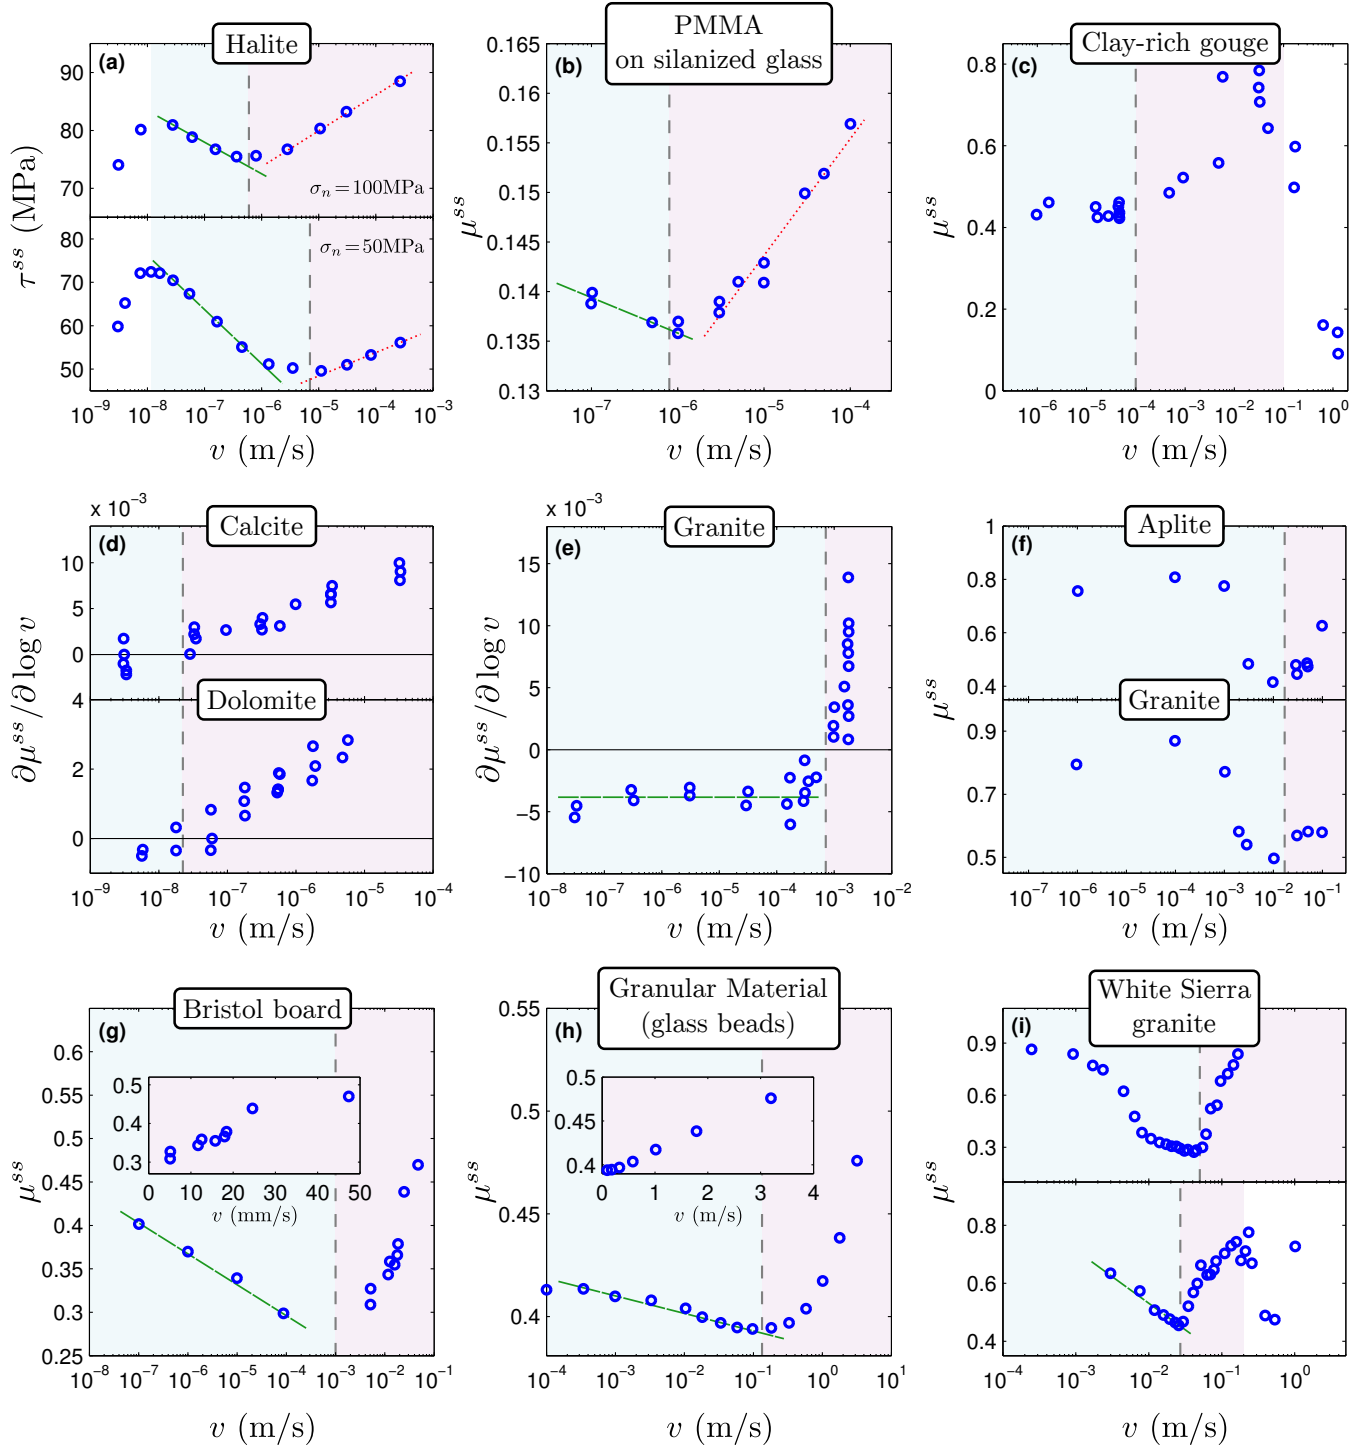


FIG. 1. **Experimental observations of steady-state velocity-strengthening friction in various materials.** In each panel the region corresponding to velocity-weakening friction (light blue background) is separated by a vertical dashed line from the subsequent region corresponding to velocity-strengthening friction (light purple background). Green dashed lines mark logarithmic SVW, while red dotted lines mark logarithmic SVS. The figure is described in detail in Section V.

mechanism for the crossover (as compared to the one discussed in the text) is involved.

- (c) $\mu^{ss}(v)$ for clay-rich gouge, data extracted from Fig. 10 of Ferri et al. [46]. The curve shows weak, quasi-logarithmic, SVW at low velocities, followed by a quasi-logarithmic SVS and then a crossover to stronger-than-logarithmic velocity-strengthening. Eventually, a sharp decrease in friction is observed at high velocities.
- (d) $\partial\mu^{ss}/\partial\log v$ for calcite (upper panel) and dolomite (lower panel), both data sets extracted from Fig. 2 of Weeks [19]. A crossover from SVW to SVS is observed ($\partial\mu^{ss}/\partial\log v < 0$ implies SVW, while $\partial\mu^{ss}/\partial\log v > 0$ implies SVS).
- (e) The same as panel (d), but for granite. Logarithmic SVW (marked by a horizontal line) and a crossover to stronger-than-logarithmic SVS are observed.
- (f) $\mu^{ss}(v)$ for aplite (upper panel) and granite (lower panel). Data courtesy of Di Toro et al. [47]. A crossover from SVW to SVS is observed in both data sets.
- (g) $\mu^{ss}(v)$ for Bristol paper, data extracted from Fig. 4 of Heslot et al. [48]. The curve shows logarithmic SVW at low velocities and a crossover to stronger-than-logarithmic SVS at higher velocities. The inset (linear v -axis) shows that $\mu^{ss} \propto v$ in the SVS regime.
- (h) $\mu^{ss}(v)$ for a granular material composed of glass beads under a very low normal stress of $\sigma_n = 30\text{KPa}$, data extracted from Fig. 2 of Kuwano et al. [41]. A clear crossover from logarithmic SVW to a stronger-than-logarithmic SVS is observed. The inset (linear v -axis) shows that $\mu^{ss} \propto v$ in the SVS regime.
- (i) $\mu^{ss}(v)$ for Sierra White granite in a rotary apparatus, data extracted from Fig. 1 of Reches and Lockner [49]. The two curves correspond to two data sets that were selected out of many sets that appeared in the original figure. The lower curve exhibits logarithmic SVW at low velocities, a crossover to stronger-than-logarithmic SVS at higher velocities and eventually SVW at very high slip velocities. The upper curve exhibits a crossover from SVW to stronger-than-logarithmic SVS.

Some other works report on SVS and its variability with various control parameters such as the normal stress σ_n . For example, Marone et al. [50] has observed SVS in experiments of simulated fault gouge. The magnitude of SVS varied inversely with the normal stress σ_n and directly with the gouge thickness and surface roughness. In this case, SVS has been associated with granular dilatancy within the gouge layer. In Kilgore et al. [51], experiments on bare ground surfaces of Westerly granite have demonstrated a crossover from SVW to SVS at

$v_m \simeq 10\mu\text{m/s}$ for a normal stress of $\sigma_n = 5\text{MPa}$. For higher normal stresses, up to 150MPa , SVS has not been observed in the range of measured slip velocities (up to $10^3\mu\text{m/s}$). It is not entirely clear whether SVS did not exist under these conditions or was simply shifted to higher slip velocities.

All in all, we believe that these diverse experimental data sets imply that the physical picture depicted above should be seriously considered.

VI. SUMMARY AND DISCUSSION

In this brief note we argued that a steady-state velocity-strengthening behavior might be a generic feature of dry friction over some range of slip velocities. We stressed that the emergence of velocity-strengthening is a natural consequence of an experimentally well-established phenomenological picture of dry friction at relatively low slip velocities. In this picture, logarithmic velocity-weakening friction (dominated by the “rejuvenation” of contact asperities) crosses over to logarithmic velocity-strengthening friction (dominated by thermally-activated rheology) at a typical slip velocity $\sim D/\phi^*$ where the real contact area saturates. We further suggested that logarithmic steady-state velocity-strengthening friction should cross over to a stronger-than-logarithmic velocity-strengthening behavior at a slip velocity v_0 , typically accompanied by a change in the dominant frictional dissipation mechanism.

The above discussed scenario is expected to hold if $D/\phi^* < v_0$. However, as D/ϕ^* and v_0 correspond to different pieces of physics, one cannot exclude the possibility that $v_0 < D/\phi^*$. In this case we expect logarithmic velocity-weakening friction to cross over to stronger-than-logarithmic velocity-strengthening friction at $\sim v_0$. Some examples in Fig. 1 seem to support this possibility. Moreover, this behavior is expected to be the generic case in athermal systems (e.g. granular materials), where no thermally-activated rheology is relevant (cf. Fig. 1h).

We compiled a rather large number of experimental data sets available in the literature, directly demonstrating the existence of steady-state velocity-strengthening friction (both logarithmic and stronger-than-logarithmic). These examples cover a rather wide range of materials, including various rocks (e.g. granite and halite), a glassy polymer (PMMA) – widely used in laboratory experiments – on smooth silanized glass, a granular material (glass beads), clay-rich gouge and Bristol board. We suspect that this behavior is robust and will be observed in many other materials as long as careful steady-state friction experiments cover a sufficiently large range of slip velocities.

We should mention two other aspects of steady-state friction that were not discussed above, but are observed in some of the data sets presented in Fig. 1. First, at extremely small slip velocities one expects friction to be velocity-strengthening due to creep-like response

[43]. This is clearly observed in panel a. At very large slip velocities thermal weakening effects might be operative, leading to significant (sometimes overwhelming) velocity-weakening friction [52–54]. This is clearly observed in panels c and i. Combining these features with the previously discussed ones, an M-like friction curve emerges. This will be discussed elsewhere as our focus here is on the crossover from velocity-weakening to velocity-strengthening friction.

The existence of velocity-strengthening friction might have serious implications for various frictional phenomena. While these have not been studied extensively in the literature up to now, we would like to mention here the effect of velocity-strengthening friction on the seismogenic zone [26], its effect on earthquake afterslip and negative stress drops [27], the role played by velocity-strengthening friction in stabilizing homogeneous sliding

between dissimilar materials [16], in facilitating slow slip events [19–25] and in giving rise to steady-state interfacial rupture fronts under stress-controlled boundary conditions [23]. Further research in this direction is called for.

ACKNOWLEDGMENTS

EB acknowledges support of the James S. McDonnell Foundation, the Minerva Foundation with funding from the Federal German Ministry for Education and Research, the Harold Perlman Family Foundation and the William Z. and Eda Bess Novick Young Scientist Fund. EAB acknowledges support of the Erna and Jacob Michael visiting professorship funds at Weizmann Institute of Science.

-
- [1] B. Armstrong-Hélouvy, P. Dupont, and C. C. De Wit, *Automatica* **30**, 1083 (1994).
- [2] C. H. Scholz, *Nature* **391**, 37 (1998).
- [3] C. Marone, *Annu. Rev. Earth Planet. Sci.* **26**, 643 (1998).
- [4] H. Olsson, K. Åström, C. C. De Wit, M. Gäfvert, and P. Lischinsky, *Eur. J. Control* **4**, 176 (1998).
- [5] B. Persson, *Sliding friction: physical principles and applications* (Springer-Verlag, 2000).
- [6] C. H. Scholz, *The Mechanics of Earthquakes and Faulting* (Cambridge University Press, 2002).
- [7] M. Urbakh, J. Klafter, D. Gourdon, and J. Israelachvili, *Nature* **430**, 525 (2004).
- [8] T. Baumberger and C. Caroli, *Adv. Phys.* **55**, 279 (2006).
- [9] Y. Ben-Zion, *Rev. Geophys.* **46**, RG4006 (2008).
- [10] H. Kawamura, T. Hatano, N. Kato, S. Biswas, and B. K. Chakrabarti, *Rev. Mod. Phys.* **84**, 839 (2012).
- [11] A. Vanossi, N. Manini, M. Urbakh, S. Zapperi, and E. Tosatti, *Rev. Mod. Phys.* **85**, 529 (2013).
- [12] M. Ohnaka, *The Physics of Rock Failure and Earthquakes* (Cambridge University Press, 2013).
- [13] J. H. Dieterich, *Pure Appl. Geophys.* **116**, 790 (1978).
- [14] A. Ruina, *J. Geophys. Res.* **88**, 10359 (1983).
- [15] J. H. Dieterich and B. D. Kilgore, *Pure Appl. Geophys.* **143**, 283 (1994).
- [16] J. R. Rice, N. Lapusta, and K. Ranjith, *J. Mech. Phys. Solids* **49**, 1865 (2001).
- [17] E. Rabinowicz, *Journal of Applied Physics* **22**, 1373 (1951).
- [18] F. Bowden and D. Tabor, *The friction and lubrication of solids* (Oxford Univ. Press, 2001).
- [19] J. D. Weeks, *J. Geophys. Res.* **98**, 17637 (1993).
- [20] N. Kato, *Earth Planet. Sci. Lett.* **216**, 17 (2003).
- [21] B. Shibazaki and Y. Iio, *Geophys. Res. Lett.* **30**, 1 (2003).
- [22] E. Bouchbinder, E. A. Brener, I. Barel, and M. Urbakh, *Phys. Rev. Lett.* **107**, 235501 (2011).
- [23] Y. Bar-Sinai, E. A. Brener, and E. Bouchbinder, *Geophys. Res. Lett.* **39**, L03308 (2012).
- [24] J. C. Hawthorne and A. M. Rubin, *J. Geophys. Res.* **118**, 1216 (2013).
- [25] Y. Bar-Sinai, R. Spatschek, E. A. Brener, and E. Bouchbinder, arXiv:1306.3658, (2013).
- [26] C. Marone and C. H. Scholz, *Geophys. Res. Lett.* **15**, 621 (1988).
- [27] C. J. Marone, C. H. Scholtz, and R. Bilham, *J. Geophys. Res.* **96**, 8441 (1991).
- [28] T. Baumberger and P. Berthoud, *Phys. Rev. B* **60**, 3928 (1999).
- [29] L. Bureau, T. Baumberger, and C. Caroli, *Eur. Phys. J. E* **8**, 331 (2002).
- [30] P. Berthoud, T. Baumberger, C. Gsell, and J.-M. Hiver, *Phys. Rev. B* **59**, 14313 (1999).
- [31] M. Nakatani, *J. Geophys. Res.* **106**, 13347 (2001).
- [32] M. Nakatani and C. H. Scholz, *J. Geophys. Res.* **111**, B12208 (2006).
- [33] O. Ben-David, S. M. Rubinstein, and J. Fineberg, *Nature* **463**, 76 (2010).
- [34] C. J. Marone, *Nature* **391**, 69 (1998).
- [35] C. Caroli, *Private communication* (2013).
- [36] J. P. Hirth and J. Lothe, *Theory of dislocations* (McGraw-Hill, New-York, 1967).
- [37] A. Kumar, *J. Appl. Phys.* **40**, 3475 (1969).
- [38] F. J. Zerilli and R. W. Armstrong, *Acta Metall. Mater.* **40**, 1803 (1992).
- [39] R. Bagnold, *Philos. Trans. R. Soc. London, Ser. A* **249**, 235 (1956).
- [40] J. Langer and M. Manning, *Phys. Rev. E* **76**, 056107 (2007).
- [41] O. Kuwano, R. Ando, and T. Hatano, *Geophys. Res. Lett.* **40**, 1295 (2013).
- [42] J. D. Byerlee, *J. Appl. Phys.* **38**, 2928 (1967).
- [43] Y. Estrin and Y. Bréchet, *Pure Appl. Geophys.* **147**, 745 (1996).
- [44] R. Stribeck and M. Schröter, *Die wesentlichen Eigenschaften der Gleit- und Rollenlager: Untersuchung einer Tandem-Verbundmaschine von 1000 PS* (Springer, 1903).
- [45] T. Shimamoto, *Science* **231**, 711 (1986).
- [46] F. Ferri, G. Di Toro, T. Hirose, R. Han, H. Noda, T. Shimamoto, M. Quaresimin, and N. de Rossi, *J. Geophys. Res.* **116**, 1 (2011).
- [47] G. Di Toro, D. Goldsby, and T. E. Tullis, *Unpublished data*.

- [48] F. Heslot, T. Baumberger, B. Perrin, B. Caroli, and C. Caroli, *Phys. Rev. E* **49**, 4973 (1994).
- [49] Z. Reches and D. A. Lockner, *Nature* **467**, 452 (2010).
- [50] C. J. Marone, C. B. Raleigh, and C. H. Scholz, *Journal of Geophysical Research* **95**, 7007 (1990).
- [51] B. D. Kilgore, M. L. Blanpied, and J. H. Dieterich, *Geophys. Res. Lett.* **20**, 903 (1993).
- [52] G. Di Toro, D. L. Goldsby, and T. E. Tullis, *Nature* **427**, 436 (2004).
- [53] J. R. Rice, *J. Geophys. Res.* **111**, B05311 (2006).
- [54] D. L. Goldsby and T. E. Tullis, *Science* **334**, 216 (2011).